

SOIL STABILISATION TECHNIQUE USING BLACK COTTON SOIL AND HUMAN HAIR FIBER

S. Kamiya¹, P. Rajendra Kumar², Dr. V. Ramesh Babu³

¹M.Tech., Scholar, Dept. of Civil Engineering, KSRM College of Engineering, Kadapa,

²Assistant Professor, Dept. of Civil Engineering, KSRM College of Engineering, Kadapa,

³Assistant Professor, Dept. of Civil Engineering, KSRM College of Engineering, Kadapa.

Abstract—Soil reinforcement technique has been used in present times to improve the shear strength of weak soils. The main objective of this study is to investigate the suitability of solid waste materials such as human hair fibers in the process of soil stabilization as a reinforcement which can replace conventional commercial fiber materials. Human hair fiber is a natural non-biodegradable waste material which creates health and environmental problems. Physical properties of soil like Atterberg's limits, compaction characteristics & strength characteristics of virgin soil samples were determined. The soil sample were treated with different percentages of Human Hair fiber (0.5%, 0.7%, 0.9%, 1.2% and 1.5%). The strength of the soil sample increased up to 1.2% and then it decreased.

Keywords: Atterberg's limits, Human hair fiber (HHF), CBR, Unconfined Compression test, Specific gravity, sieve analysis.

1. INTRODUCTION

Expansive soils always pose challenge to foundation engineering. In India, these soils occupy around 20% of the total area. When geotechnical engineers are faced with swelling type of soils, it is great challenge to foundation engineers. The design of foundations and pavements founded on swelling soils always involve a certain degree of risk and damage. The characteristics that are of concern to the design engineers are permeability, compressibility and durability. The test results such as Atterberg's limits, compaction, California bearing ratio and strength characteristics obtained in expansive soils admixed with human hair fiber at varying percentages of 0.5%, 0.7%, 0.9%, 1.2% and 1.5% of the expansive soil. The purpose of this study is to investigate the influence of human hair fiber on the geotechnical properties of an expansive soil. This paper focus on experimental test plan was to investigate the effect of HHF on strength improvement of expansive soil. K. Shankar Narayanan and S. Mary Rebakh Sharmila (2017) conducted research on "stabilisation of clay with human hair fiber". They studied to improve the shear strength parameters. They found that uncompressive strength of soil was increased at 1.2% of HHF. The CBR value increased at 1.2% of HHF. Renju R Pillai et al. (2012) studied on "Innovative technique of improving the soil using human hair fibers". They found that the engineering properties of soil increased by adding HHF. The liquid limit increased, plastic limit decreased and moisture content increased and maximum dry density decreased due to the addition of HHF. The Unconfined compressive strength value increased upto 2 times that of unreinforced soil. Wajid Ali Butt et al. (2014) studied on "Soil Sub-grade improvement using Human hair fiber" and

concluded that the CBR value increased by adding HHF and attains maximum value at 2% of fiber. Fibers of different length and equivalent diameter were used with aspect ratio of 295 to 500. Prakash Patil et al. (2016) studied on "Innovative method of improving subgrade strength of soft soil using Human Hair fibers as reinforcement" and concluded that by adding HHF the subgrade strength of clay soil was improved. They use fibers having average length of 20mm. The CBR value has increased at 0.1% of HHF. The compressive strength also attains maximum value at 0.1% of HHF. Rohin Kaushik (2014) studied on Innovative technique of improving the CBR Value of soil using hair fiber and flyash by using different proportions of human hair fibers at 0.5, 1.0 and 1.5 by percentage and observed that there was increase in the bearing ratio of the soil, CBR value got increased at 1.5% of HHF. Tom Elias et al. (2016) studied on comparison of soil stabilisation with Human hair fiber and lime. They found that strength was increased with optimum percentage of HHF and lime added together. The strength value increased with 9% of lime and 1.5% of hair fiber mixed together. Sanjay Choudary et al. (2012) studied that the effect of Human hair fiber is mixed with polypropylene at different percentages as rolled mills. They have better flexural and impact strength. They observed that the tensile properties were increased with percentage of Human hair fiber along with different resins. Anjanadevi K.A et al. (2019) studied on "stabilisation of clay using jute and Human hair fiber". They observed that the maximum dry density value has maximum value at 0.5% of jute and 1% of HHF and has OMC decreases. The UCC value was increased. The CBR value was increased with a mixture of 1.5% of hair and jute. Sonu Singh et al. (2018) studied that subgrade properties of soil increased with addition of HHF. They conduct experiments of soil with fiber by using CBR and triaxial test. The CBR value has increased with inclusion of 1% HHF. J.N. Akhtar and Sh. Ahmad (2009) studied the effect of mixing of hair fiber on mechanical properties of flyash. They done experiments to determine effect of randomly oriented hair fiber on mechanical properties of flyash based hollow block. The compressive strength increases at 2% of fiber content.

2. MATERIAL INVESTIGATION

2.1 Expansive soil:

Soil sample was collected from paidikalva village, near Krishnapuram kadapa, A.p, India. From 3 meter depth below the

natural ground level,the samples were collected. The soil classified as 'CH' as per I.S.Classification (I.S.1498:1978)



Fig1:Expansive soil

Table1:Basic properties of the soil

S.NO	Properties of soil	Values
1	Grain size distribution:	
	(a)sand	17%
	(b)silt	19%
	(c)clay	64%
2	Atterbergs limits:	
	(a)Liquid limit	83%
	(b)Plastic limit	39%
	(c)Plasticity index	46%
3	IS Classification	CH
4	Free swell index	140%
5	Specific gravity	2.58
6	Compaction Characteristics	
	(a)Maximum Dry unit weight	1.62g/cc
	(b)Optimum Moisture Content	20.83%
7	California Bearing Ratio Value	2.48%
8	Unconfined Compressive Strength At Proctor Density	1.36kg/cm ²

2.2 Human hair fiber:

From local sources, the human hair was collected.It can be used as a reinforcing agent to minimize environmental problems.To obtain the average diameter of human hair fiber,Scanning electronic microscope analysis was conducted.By adding fibre content of 0.5%,0.7%,0.9%,1.2% and 1.5% by weight of soil, samples were prepared. Figure 1.2 show fibers used in this study.Figure1.3 shows the SEM images of human hair fibers.



Fig 2:Human hair fiber

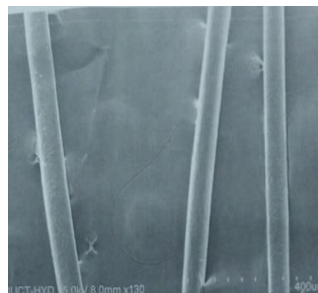


Fig 3:SEM Image of hair

Table 2:Properties of Human Hair Fiber

PROPERTY	SPECIFICATIONS
Length	4mm-40mm
Diameter	40µm-111µm
Protein present	Keratin
Cross section	Circular
Outer Covering	Cuticle
Tensile strength	Equal to copper wire of similar Diameter
Elongation	1.5 times by its dry weight

2.3 Sample preparation:

Here,the commercial grade human hair fiber (HHF) used as a stabilizer.HHF added at 0.5%,0.7%,0.9%,1.2% and 1.5% by weight of soil.The quantity of fiber computed corresponding to the above percentage directly mixed to soil before water adding to it.in order to obtain even distribution of fiber.

The various laboratory tests were conducted on virgin soil samples as per IS standard (IS:2720) to determine its Index and Engineering properties.The soil sample is mixed with various percentages of human hair fiber.Compction characteristics i.e.,maximum dry density and optimum moisture content were determined by standard proctor test results.Addition of fibers was done carefully and percentage is calculated by weight.

2.4 Laboratory Tests and Program:

As Per Codal procedure using Casagrande's apparatus the atterberg's consistency limits(liquid limit and plastic limit) were determined. With human hair fibers of different proportions, the tests were carried out on the soil. To determine the maximum dry density(MDD) and the optimum moisture content(OMC) of both unreinforced and reinforced soils, Proctor's standard compaction test was carried out and with various moisture content the fibers were thoroughly mixed with soil. To determine the compaction properties of the unreinforced soils and proctor compaction properties of the black cotton soil mixed with human hair fiber of different percentages. For bc soil and human hair fibers of various proportions compacted to their maximum dry density(MDD) and optimum moisture content(OMC), Unconfined compressive strength tests were conducted and by compacting the sample in mould using hammer in three equal layers with 25 blows per layer,cylindrical specimens were prepared.At an average MDD and OMC of 1.62g/cc and 20.83%,all specimens were prepared.The mix proportions of OMC and MDD do not vary to great extent.The unreinforced and fiber reinforced specimens were thus avoided due to effects caused by differences in dry density and water content.

3.RESULTSANDDISCUSSIONS

3.1Effects on Consistency Limits:

There is reduction in liquid and plastic limit of soil with addition of fiber upto 0.9%.Beyond that it has been observed that there is increase in LL and PL.The influence of fiber on plasticity index is considerable upto 0.9% human hair fiber admixed soil.

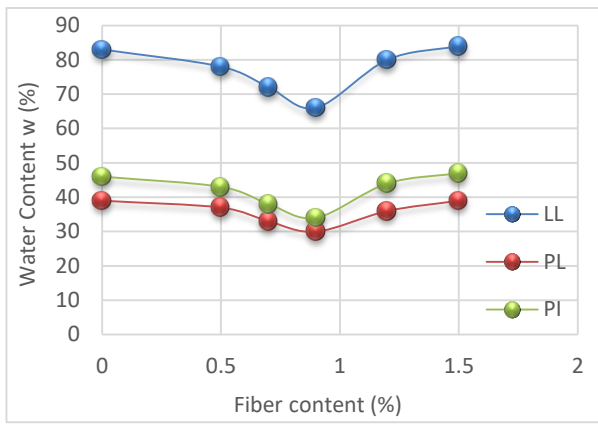


Fig 4:Variation of Consistency Limits

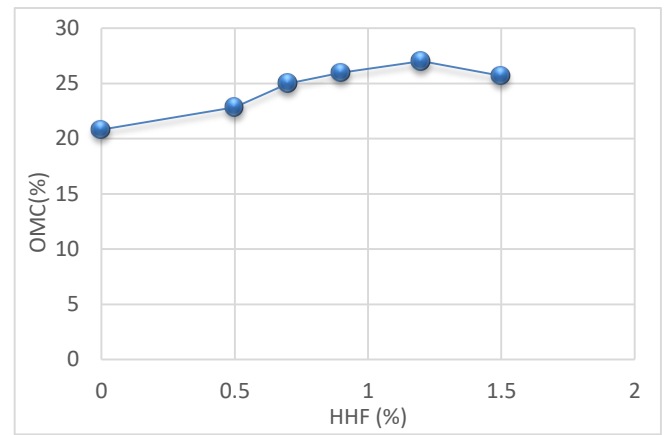


Fig 6:HHF% vs Corresponds optimum moisture content

3.2 Effects on Compaction Characteristics

From fig5,6&7 the decrease in dry density with increase in fibre percent as usual the water content may be increases with respect to percentage of fiber admixed soil upto 1.2% of HHF admixed soil .with addition of 1.2% of HHF the optimum water content increased to 27.02%,beyond that it decreases and the dry density decreased to 1.52%, beyond that it increases. Hence it is concluded that at 1.2% of HHF, Optimum water content increases i.e.,27.02% and dry density decreases i.e.,1.52%.

3.3 Effects on California Bearing Ratio & Unconfined Compression Strength

It was observed that from the fig8 CBR value of soil samples admixed with HHF increase with increase in percentages of HHF upto 1.2% HHF admixed soil and it was found that the excess of HHF more than 1.2% causes decrease in CBR value.

From the fig9&10 unconfined compressive strength was observed in terms of additive percentage better shear strength observed at 1.2%. Index properties and compaction characteristics reveals 1.2% HHF admixed soil is better strength achieving percentage.

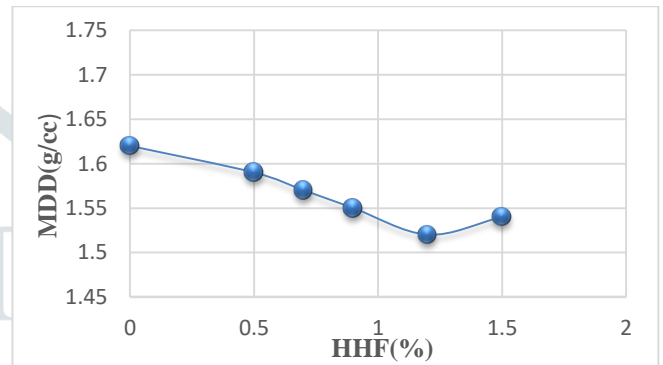


Fig 7:HHF% Vs Corresponding Dry densities

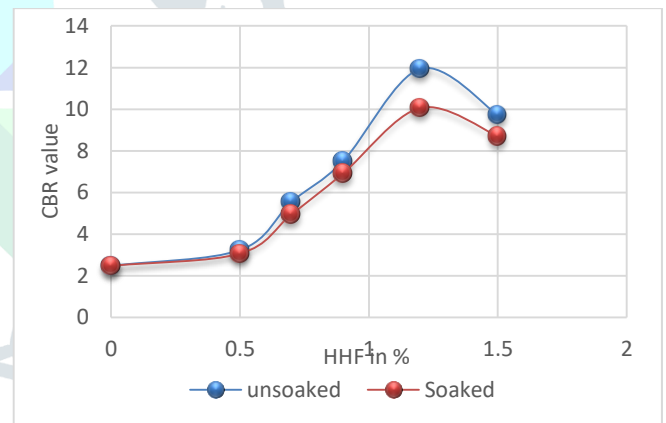


Fig 8:CBR values for un-soaked and soaked conditions for HHF admixed soil

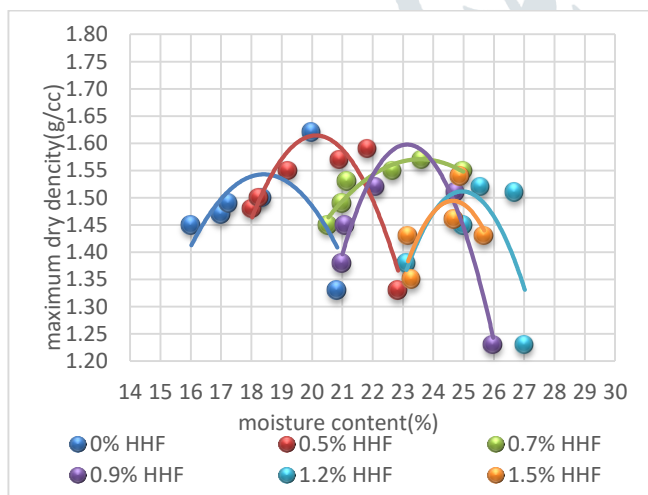


Fig 5:Moisture content vs Dry density for HHF Admixed soil

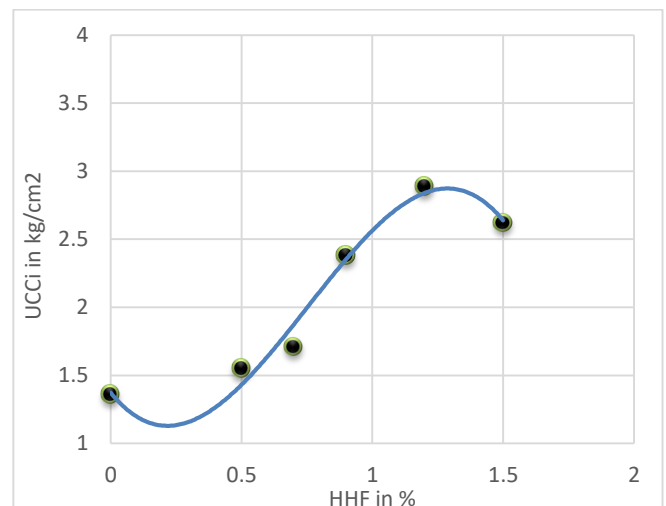


Fig 9:HHF Vs UCC strength

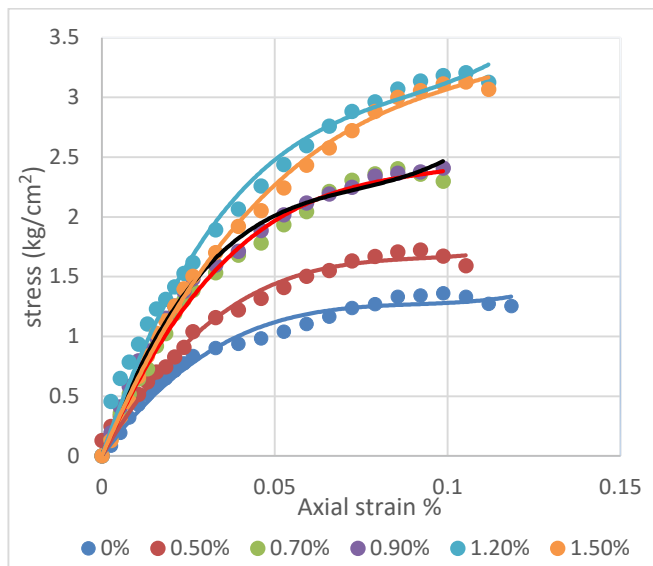


Fig 10: Stress vs Strain

5. CONCLUSIONS

1. The liquid limit value first decreases and then increases at 1.2% of HHF.
2. The unsoaked CBR has maximum value at 1.2% of HHF.
3. The UCC strength of unreinforced and reinforced soils are substantially different with addition of 1.2% of fibers by weight. The UCC value increased up to 2.3 times of unreinforced soil.

ACKNOWLEDGEMENT

The author acknowledges the support of Director, Principal and all the Civil Engineering Staff of KSRM College of Engineering, Kadapa.

REFERENCES

1. K.Shankar, Narayanan, S.MaryRebekahsharmila(2017), "Soil Stabilization Using human hair fibre" International journal for emerging research and development, vol.1, Issue2, PP.89-94.
2. Renju R Pillai and Ayothiraman Ramanathan(2012): "An innovative technique of Improving the soil using human hair fiber. "Advancing civil, Architectural and construction Engineering and Management. July 4-6-2012 Bangkok, Thailand.
3. Wajid Ali Butt et al, "Soil sub grade improvement using human hair fiber" International Journal of Scientific and Engineering Research, Volume 5, Issue 12, DEC 2014.
4. Prakash Patil and Harini H.N (2016): "Subgrade strength of soil using human hair fibres as reinforcement" IJSRSET, vol.2, Issue4, PP.551-554.
5. Rohin Kaushik(2014): "Innovation technique of improving CBR value of the soil using Hair fibre", Global Journal of Engineering Science and Researches, ISSN2348-8034, PP.1-6, June 2014.
6. Tom Elias et al(2016), "comparative study of soil stabilisation using human hair and lime", IJSER, volume7, Issue2, ISSN2229-5518, PP.1323-1326, Feb 2016.
7. Sanjaychaudary, Bhavana Pandey(2012), "Mechanical behaviour of polypropylene and human hair fibers and

polypropylene reinforced polymeric composites", IJMIE, ISSN No.2231-6477, vol2, Issue-1, PP.118-121, 2012

8. Anjanadevik.A(2019), "Soil stabilisation using jute and human hair fibers", IRJET, vol-6, Issue-5, PP-5117-5121, May 2019.
9. Sonu Singh et al(2018), "Characterization of clay soil reinforced with human hair for pavement design", (ICRTESSM-18), ISBN:978-93-87793-12-5, PP-212-218, March 2018.
10. J.N.Akhtar et al(2009), "The effect of randomly oriented hair fiber on mechanical properties of flyash based hollow block for low height masonry structures", pp-221-228, AJCE, Vol-10, No.2.
11. Rajesh Prasad Shukla, Niraj Parihar, Pravara Yadav, Nitesh Mankotia(2015), "Problems and treatment of black cotton soil", 50th Indian Geotechnical Conference.
12. Manchikanti Srinivas, G.V, R.Prasad Raju(2009), "XRD and SEM studies of chemically Treated Expansive Soil subgrades", Indian Geotechnical Conference IGC INDIA..
13. Abdelkadar Zerrouk, Belkacem Larmri, C.Vilupanadan and Said Kenai(2016): "Performance of human hair fibre reinforcement on stabilised clay".

Author Profile



Syed Kamiya received B.Tech. Degree in Civil Engineering from J.N.T.U in 2017. She is pursuing M.Tech in Geotechnical Engineering, K.S.R.M College of Engineering. Her areas of interest are soil stabilisation and strength of materials.



P. Rajendra Kumar working as Assistant Professor at K.S.R.M College of Engineering. He has received his M.Tech in Rock Engineering and Underground Structures at IIT Delhi. His areas of interest are Tunnel Design, Slope Stability in rock and soil, Foundation Engineering, Soil Stabilizations, and Ground Improvement Techniques.



Dr. V. Ramesh Babu working as Assistant Professor at K.S.R.M College of Engineering. He has received his Ph.D., in the year 2019 from JNTUA, Anantapur. His areas of interest are Structural Analysis, Strength of Materials, RCC, Engineering Mechanics.